

Review

Open Access

Extracellular scaffold design for ultra-soft microtissue engineering

Jiaqi Wang^{1,2}, Xiaowei Tang^{1,2}, Zitian Wang^{1,2}, Jiawei Li^{1,2} and Shaohua Ma^{1,2*}

Abstract

Soft and ultra-soft extracellular scaffolds constitute a major fraction of most human internal organs, except for the skeletal system. Modelling these organs *in vitro* requires a comprehensive understanding of their native scaffolding materials and proper engineering approaches to manufacture tissue architectures with microscale precision. This review focuses on the properties of soft and ultra-soft scaffolds, including their interactions with cells, mechanical properties (e.g. viscoelasticity), and existing microtissue engineering techniques. It also summarises challenges presented by the conflict between the properties of the materials demanded by cell behaviours and the capacities of engineering techniques. It proposes that leveraging the engineering ability of soft and ultra-soft scaffolds will promote therapeutic advances and regenerative medicine.

Introduction

It has been over a century since the first techniques utilizing cell culture *in vitro* were reported. In 1907, Ross Harrison isolated and cultured a small piece of living frog embryonic tissue in a hanging drop¹. Later, scientists developed the classic 2D monolayer cell culture system. However, they were not able to mimic *in vivo* states on plastic Petri dishes because tissue-specific architecture, cell-cell interactions, and cell-matrix interactions are lost in the process. The obvious drawbacks of 2D cell culture have led scientists to develop 3D cell culture techniques. As early as 1972, the first 3D cell culture system *in vitro* was reported using collagen as the extracellular scaffold². Bard and Elsdale compared the differences between cell morphology, growth, and behaviour under 2D and 3D cell culture conditions and revealed the striking similarity of cells in the 3D culture system and *in vivo*. It is well

accepted that 3D cell culture technologies are becoming essential for drug screening, tissue engineering, and other translational research.

The extracellular matrix (ECM) plays a pivotal role in 3D cell culture, and many natural and synthetic scaffolds provide various culture conditions that have different desirable properties, including stiffness, biodegradability, porosity, and cytocompatibility³. Matrigel is among the most ubiquitous natural scaffolds in 3D cell culture, with an average elastic modulus of ~650 Pa⁴. It is a basement membrane matrix extracted from Engelbreth-Holm-Swarm murine sarcoma, first developed in 1977⁵. Matrigel provides the desired mechanical properties, sufficient cytocompatibility, biomimicry to native ECM, and the ability to promote cell adhesion and differentiation across many cell types⁶.

However, the applicability of Matrigel is severely limited by the variability in its composition and the presence of xenogeneic contaminants. Therefore, chemically defined native-based or synthetic-based xeno-free alternatives are in great demand. The wide acceptance of Matrigel in the last few decades may partially be

Correspondence: Shaohua Ma (ma.shaohua@sztsinghua.edu.cn)

¹Institute of Biopharmaceutical and Health Engineering (iBHE), Shenzhen International Graduate School (SIGS), Tsinghua University, Shenzhen 518055, China

²Tsinghua-Berkeley Shenzhen Institute (TBSI), Shenzhen 518055, China

These authors contributed equally: Jiaqi Wang, Xiaowei Tang

© The Author(s) 2021



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

attributed to the lack of other scaffolds that are easy to use and versatile for culturing different types of cells. Recently, some synthetic materials have shown comparable or superior outcomes in 3D cell culture, tissue engineering, and organoid-based studies of both development and diseases^{7–10}.

In this review, we begin by discussing the importance of three endowed and desired properties of extracellular scaffold design: mechanical properties, cell-matrix interactions, and spatiotemporally “programmable” stimuli responsibility. We then briefly summarise the engineering approaches that take advantage of these properties, such as microfluidics, electrospinning, photolithography, and microextrusion (Fig. 1). We propose the term *microtissue engineering*, which refers to the techniques that formulate small-scale (e.g. smaller than a few millimetres) artificial tissue structures with microscale precision. We refer to ultra-softness as the modulus range below a few kilopascal, which is the typical stiffness of many soft tissues, including the brain, lung, liver, and skin, as well as their reconstituted extracellular matrices. Finally, we discuss the current impediments to rational design and manufacturing of extracellular scaffolds with microscale precision and

provide our perspective on the future of engineering scaffolds for cell culture applications and translational research.

Mechanical properties

To understand the different behaviours of cells in 2D and 3D culture conditions, biologists were intently focused on deciphering signal transduction pathways, until they realised that not only receptor binding but also physical entanglements of cells and their surrounding scaffolds would also alter critical cellular events¹¹. Pelham et al. demonstrated that substrate stiffness could affect cell adhesion, morphology, and locomotion by using polyacrylamide hydrogels with varying elastic moduli as the supporting scaffolds¹². Since then, many studies have found that ECM stiffness affects cell behaviours from a range of dimensions and plays a key role in regulating development, homeostasis, regenerative processes, disease progression, and cell response to drugs. However, tissues are not purely elastic materials, like rubber or a spring. They exhibit a time-dependent mechanical response and dissipate a fraction of the energy that deforms them, a property called viscoelasticity or poroelasticity, depending

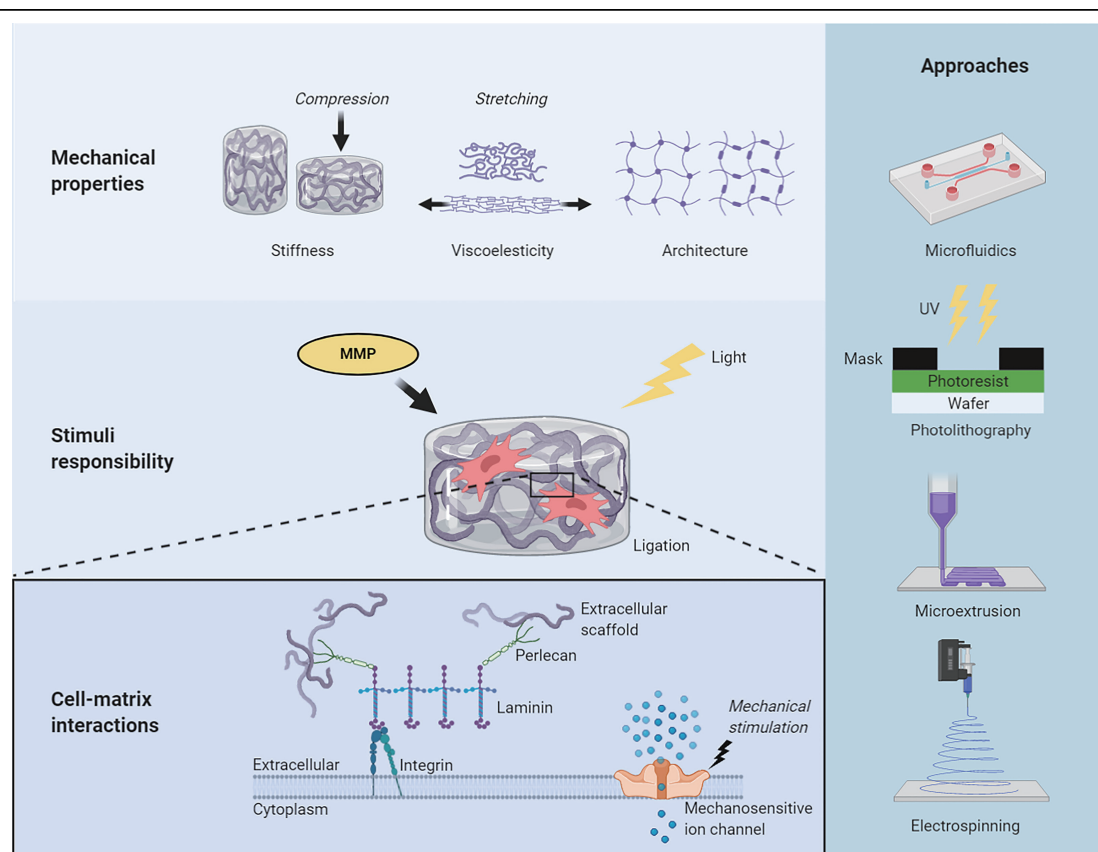


Fig. 1 Summary of cues provided by extracellular scaffold and their engineering techniques.

on the molecular mechanism¹³. Architectural features and external forces have also been reported to affect various aspects of cell behaviour. These findings improve the current stiffness-centric view of cell-matrix mechano-transduction and challenging *in vitro* modelling.

The stiffness of the scaffold, or as referred in biomaterial design, the elasticity of the material, has been of great concern once the subject is established. Cell lineage proliferation and differentiation, especially pluripotent stem cells (e.g. embryonic stem cells [ESCs] and induced pluripotent stem cells [iPSCs]), are highly sensitive to scaffold stiffness^{14–16}. Directed stem-cell differentiation may be achieved by reconstituting the stiffness of the natural tissue environment with an engineered scaffold: soft scaffolds that mimic the elastic modulus of the brain (0.1–1 kPa) can be neurogenic; scaffolds of intermediate stiffness that mimic skeletal muscle (8–17 kPa) can be myogenic; and rigid scaffolds that mimic bone (25–40 kPa) are osteogenic¹⁷.

Natural materials, such as collagen and Matrigel, may have an inherent inability to decouple their biochemical and mechanical properties. These biological materials are not only very soft (Young's modulus $E < 1$ kPa) but are difficult to characterise. They may suffer spatiotemporal heterogeneities in both biological and mechanical properties because of their complex composition or poorly controlled solidifying processes. The uses in both basic research and translation have been hampered by batch-to-batch inconsistency and lack of tunability. Murphy et al. tested the elastic modulus of Matrigel using atomic force microscopy (AFM). They reported an average modulus of approximately 450 Pa¹⁸. However, they observed a static measurement deviation of 840 Pa in the same sample, which could be attributed to the intrinsic inhomogeneity in spatial composition and the probed micromorphology in the measurement. Mechanical imaging interferometry was applied to obtain point mechanics of the surface layers of the Matrigel⁴. The median value of 650 Pa was consistent with bulk measurements; however, on the microscale, the films were heterogeneous and contained regions distinctly stiffer than their surroundings, which varied within the range of 1–2 kPa. Therefore, mechanically tunable and chemically defined synthetic alternatives have been proposed to overcome the limitations of Matrigel.

Viscoelasticity, a historically ignored property in biomaterial design, is accepted as another key feature of biomaterials¹³. Living cell activities *in vivo* and 3D cell culture *in vitro* are dynamic processes, including cell-matrix interactions, cell-cell interactions, and time-dependent scaffold manners, such as creeping, stress loading, and relaxation. Viscoelasticity is a near-universal


feature of living tissues and native ECMs, but not of some widely used synthetic materials, such as polyacrylamide (PAM) hydrogels and polydimethylsiloxane (PDMS) elastomers, which are linearly elastic. In linear elastic materials, stress is linearly related to strain for small strains, with no loss of mechanical energy and reversible deformations. In comparison, viscoelastic materials exhibit stress relaxation in response to constant deformation and increased strain, or creep, in response to constant stress.

Matrix viscoelasticity regulates cell fate in 3D cultures. For example, stress-relaxing hyaluronic acid-collagen hydrogels promote cell spreading, fibre remodelling, and focal adhesion formation¹⁹. Faster stress relaxation and increased loss promote cell cycle progression and completion of mitosis in single cancer cells and fibroblasts, as well as osteogenic differentiation of mesenchymal stem cells (MSCs)²⁰. Darnell et al. used the RNA-seq method to reveal the transcriptional responses of cells in 3D culture to stress relaxation, matrix stiffness, and adhesion ligand density. They exhibited substantial independent effects and coupling among these properties, demonstrating clear cell-type and context-dependent viscoelasticity sensing¹⁶.

Microtissue engineering is fundamental for organoid manufacturing. Architectural features, including geometry, porosity, and topology, as well as external forces, determine the tissue shape and growth kinetics. Geometry is a well-known factor that controls cell proliferation and organoid formation under 3D culture conditions. Lawlor et al. changed kidney organoid length while maintaining the same absolute number of starting cells. The results showed that the width-to-length ratio changes in organoid conformation affected organoid morphology, increasing the abundance of nephrons, conformation, and maturity of epithelial structures²³ (Fig. 2a–c). Porosity, including the scaffold pore distribution, is another architectural factor that critically determines the growth rate and nature of vascular sprout branching, while stromal cells promote hypoxia signalling and secrete chemokines to promote this outcome²⁴. External forces after gelation are influenced by different mechanical cues from the internal stiffness of the scaffold. Li et al. showed that volumetric compression regulates the growth of intestinal organoids by modifying intracellular crowding and elevating Wnt/ β -catenin signalling²² (Fig. 2d, e).

Cell-matrix interactions

Cells sense the extracellular environment in many ways, including integrin- and syndecan-based cell adhesion, conformational changes in mechanosensitive proteins (e.g. talin, vinculin, or lamin), activation of mechanosensitive ion channels (e.g. Piezo1), localisation of mechanosensi-

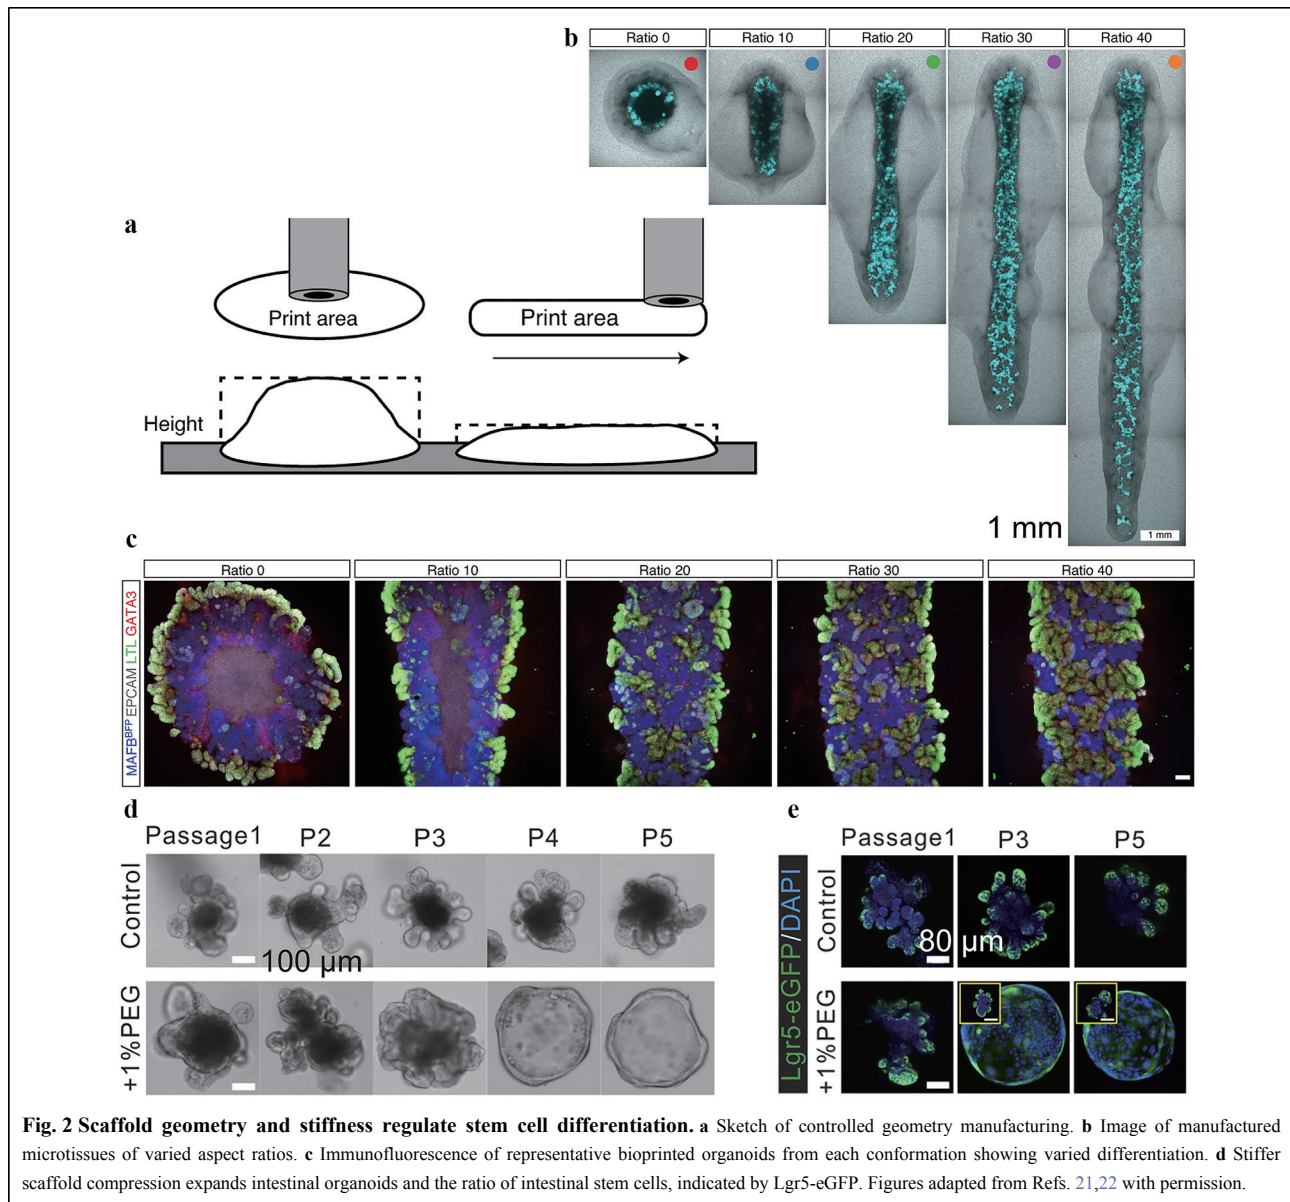

tive proteins (e.g. YAP/TAZ), and downstream activation of transcriptional factors. The cell-matrix interactions crucial for cell fate regulation and proliferation can be selectively reconstructed on synthetic scaffolds by incorporating cell-adhesion motifs. Fibronectin-derived three-amino-acid peptide Arg-Gly-Asp (RGD) is one of the most ubiquitously used peptides to promote cell adhesion to synthetic scaffolds. It binds to $\alpha\beta3$ and $\alpha\beta5$ integrins. The cyclic form of RGD, cyclo (Arg-Gly-Asp-d-Phe-Lys) (cRGDfK), was identified as an effective peptide for iPSC culture and performed favourably compared with other peptides derived from laminin, fibronectin, and vitronectin²⁵. Lamshead et al. reported that iPSCs could be maintained for ten passages on cRGDfK brush-coated poly

(acrylamide-co-propargyl acrylamide) (PAPA) substrate²⁶.

Synthetic scaffolds have also been used to mimic the role of heparin sulfate proteoglycans, such as perlecan, to support iPSC culture^{27–31}. Klim et al. conducted surface display experiments to identify the ability of different peptides to sustain cell adhesion, including growth factor receptor-binding peptides, integrin-binding peptides, and heparin-binding peptides derived from various structural proteins. The results showed that the heparin-binding peptide GKKQRFHRNRKG derived from vitronectin supported cell adhesion at the lowest peptide substitution levels. Furue et al. developed a defined serum-free medium for ESC maintenance and proliferation on a type of I-collagen substrate in the presence of heparin. They found

that ESCs proliferated in the absence of exogenous FGF-2 if heparin was also present²⁸. Similarly, Nowak et al. showed that poly(ethylene glycol)-heparin (PEG-HEP) matrices could promote the development of human mammary epithelial cells (MECs) into polarised MEC acini *in vitro*³¹. Cell remodelling in the post-processing stage generally increases the tissue strength by 1–2 orders of magnitude³².

Mechanosensitive activation of ion channels and other protein effectors is also considered while designing the extracellular scaffold. Yes-associated protein 1 (YAP) nuclear translocation, regulated by mechanical cues, activates downstream transcriptional pathways. YAP/TAZ is a key mediator of mechanosensitive signalling; YAP/TAZ nuclear-to-cytoplasmic ratio is a marker of YAP/TAZ activity, sigmoidally responding to scaffold stiffness. The HAVDI peptide from N-cadherin reduces the mechanical threshold for YAP/TAZ signalling, thus altering MSC interpretation of substrate stiffness¹⁵. However, it is not fully clear how YAP/TAZ signalling is regulated by the complex interplay of microenvironmental factors (e.g. stiffness and degradability) and culture dimensionality.

Crosslinking choices

In the fields of tissue engineering and regenerative medicine, cells are distributed with certain precision levels (e.g. a few tens to hundreds of microns) before implantation and integration with native tissues^{33,34}. Cell self-organization, together with scaffold remodelling, further improves organotypic structure development at single and multi-cellular levels^{35,36}. Scaffold engineering is generally accompanied by controlled sol-gel transition and is strategized with the intrinsic cross-linking properties of the materials, including the reaction mechanism, rate, temperature, and initiation conditions.

A class of materials undergoes sol-gel transition by varying the temperature during molecular assembly. Gelatin, a widely used proteinaceous material derived from natural resources, is solid at temperatures below 30 °C, but liquid at 37 °C^{37,38}. Matrigel, also naturally resourced and comprised of protein and proteoglycan mixtures, is liquid at 4 °C but crosslinked at elevated temperatures⁶. The sol-gel transition is reversible. Gelatin is functionalized with methacrylate groups for further photocrosslinking³⁹, or irreversibly cross-linked by a transglutaminase-accelerated reaction⁴⁰, to improve its thermostability.

Other chemical crosslinking mechanisms have also been employed in the engineering of tissue scaffolds. For example, glutaraldehyde⁴¹ and genipin⁴² can rapidly crosslink proteinaceous materials and their derivatives.

However, due to their cytotoxicity, these reactions are mostly used in acellular scaffold engineering, followed by cell seeding, flow-induced cell infiltration, or directed cell migration^{43,44}. Click reactions offer mild and cytocompatible crosslinking choices, although the reacting components are mostly synthetic or require chemical functionalization⁴⁵. Divalent ion-induced crosslinking is a class of materials that form chelation nodes between the scaffolding molecular chains and ions, such as Ca²⁺ and Ba²⁺ (Refs. 46,47). Crosslinking is rapid and reversible by extracting ions from a scaffold with a stronger ion-chelating agent.

Stimuli responsibility

The concept of 4D printing has attracted considerable interest since it was introduced by Skylar Tibbits in 2013⁴⁸. 4D printing emphasises post-printing transformation over time or its shape-changing ability⁴⁹. The stimuli could be either internal molecules secreted by cells or external signals given by researchers, such as light, heat, ligand, and/or pH shifting. The scaffold needs to be ‘plastic’ and deformed at certain levels during cell culture, contributing to the reconstruction of the extracellular niche and directing the cellular processes. Reconstituted ECM materials used for cell culture, including type-1 collagen gels, Matrigel, and fibrin gels, are typically viscoplastic, unless they are sufficiently crosslinked. In contrast, non-degradable polymer networks would build up stress during cell growth and proliferation and alter cell spreading and migration.

Light is a common stimulus used in laboratories and can be administered remotely. Light initiates strengthened crosslinking, which increases the scaffold modulus or triggers the cleavage of covalent bonds to reduce scaffold stiffness. Stem cell differentiation lineage can be altered via *in situ* mechanical tunability, and the level of alteration, or plasticity, is negatively correlated with the time point of interference on the scaffold mechanics^{50,51}. Other post-fabrication stimuli include ligand density and ligating abilities. Cells can modify their niche by secreting enzymes, such as matrix metalloproteinases (MMPs). Consequently, MMP-cleavable peptide modification is a technique widely used in scaffold design. MMP-sensitive gels improve ESC proliferation⁵². Local administration of MMP inhibitors can attenuate scaffolding degradability and cell remodelling in myocardial infarction⁵³.

Scaffold shaping choices

Filling microstructure moulds with liquid materials produces shaped scaffolds with microscale precision after material crosslinking^{54,55}. Both solid and liquid shapes (e.g. drops) can be used to engineer moulds. The shapes of

liquid moulds are defined by volume, surface tension, and external forces, including gravitational force, adhesion force with the substrate, and viscous force. However, **static moulding** has intrinsic limitations, including low production capacity and poor structural recovery of soft materials. Various **dynamic moulding** approaches have been developed to engineer the required structures.

Static moulding of soft microbeads

Static moulding to shape microgels requires a simple operation, whereby the fluidic precursor solution is cast into the moulds, in which it undergoes *in situ* crosslinking^{55,56}. Static moulding enables slow crosslinking reactions, but the production is limited to simple patterns and does not permit distinctive interfaces between different phases. Moreover, the structural recovery of soft microbeads remains challenging.

Lyophilisation has been introduced in static moulding operations to improve structural integrity and pattern complexity. For example, hyaluronan (HA) scaffolds have been obtained with defined shapes and parallel-oriented microchannels by lyophilizing the casted HA solution in the molds⁵⁷. The microchannel was oriented along the axis of the mould. However, the production rate is still limited, particularly for tissue engineering with microscale precision. Additionally, lyophilisation is not compatible with cell-laden manipulation.

Dynamic moulding of microbeads in microfluidics

Microfluidics can adopt continuous and discrete flow methods, that is, droplet-based microfluidics^{60,61}. This depends on the nature of the microflows and their wettability with the microchannels. Both microchannels and droplets can be employed as structural moulds to generate fibres and various microbeads.

Monodisperse microbeads are produced using microfluidics droplets as structural templates for crosslinking⁶⁰. The shapes are dominated by the droplet surface tension when crosslinking occurs under static conditions. At the microscale, the gravitational force is negligible. Surface tension determines that mono-phasic droplets remain spherical throughout crosslinking, thus generating microspheres⁶². When droplets are multiphasic, the spherical shape is compromised by the joint surface tension among the multiple discrete phases and the continuous phase^{63,64}. Moreover, the multi-phases within individual droplets can be selectively crosslinked, generating microbeads that adopt concave, convex, or even sharps^{61,65}.

Microfluidic droplets are usually enclosed with surfactant molecules on interfaces to maintain their

stability before crosslinking⁶⁶. For tissue culturing, it is necessary that the microbeads are removed from the surfactant molecules through repeated washing. When the materials are extremely fragile under shear conditions, such as collagen and Matrigel beads, surfactant removal may render their structural recovery challenging.

Channel confinement allows the production of non-spherical microbeads, such as pancakes and rods. Rapid crosslinking materials can be engineered in short regular channels (e.g. a few centimetres long). Most soft and ultra-soft materials possess slow crosslinking properties, thereby requiring metre-long channels for crosslinking. Meanwhile, minimal disturbance is required during the transition and transport of droplets and beads. Therefore, this requirement is fulfilled with a single long tubing or a cascade of tubing connections with nearly zero dead volumes at the connection ports. Moreover, when channel confinement is effective, the droplet (or bead) occupies the entire interior cross-section of the tubing (channel), thus preventing the bypass of the continuous phase (usually oil). It ensures stable separation and avoids droplet-droplet (and bead-bead) collisions, thus eliminating surfactant-dependent droplet stabilisation, and suits the production of extremely fragile structures^{38,58,59}. In addition, the viscosity ratio across the droplet-oil interface can regulate the molecular mixing in droplets, thus offering a route to control the reaction kinetics in a non-chemical way⁵⁸ (Fig. 3a–c).

High hydraulic resistance accompanies in-channel crosslinking in long tubing, as the resistance is proportional to the length of the sol-gel transition. To overcome high resistance, fluids should be pumped using high pressure, which may result in high stresses that are detrimental to cells and cause system failure. When cells are encapsulated in droplets for microtissue engineering, mild stress conditions are preferred. Hydraulic resistance can be reduced by employing low-viscosity oil, which generates low friction with the channel walls⁶⁷. In addition, low-viscosity oil as the continuous phase contributes to milder flow conditions, that is, lower magnitudes of shear and stress levels, in droplets^{68,69}.

In cascade tubing microfluidics, various microtissues adopting spherical, plugged, and segmented organisations can be produced using mammalian cell-favoured materials, such as collagen, Matrigel, and fibronectin, in their native states^{6,70,71}. It promotes cell proliferation, differentiation, and self-organization, thus offering optimised access to uniform organoids, tumoroids, and their controlled assembly^{36,72}. As many human organs are ordered assemblies of microscale structural and functional repeating units³⁴, such engineered microtissues can be cultured *in vitro* to function as development and disease

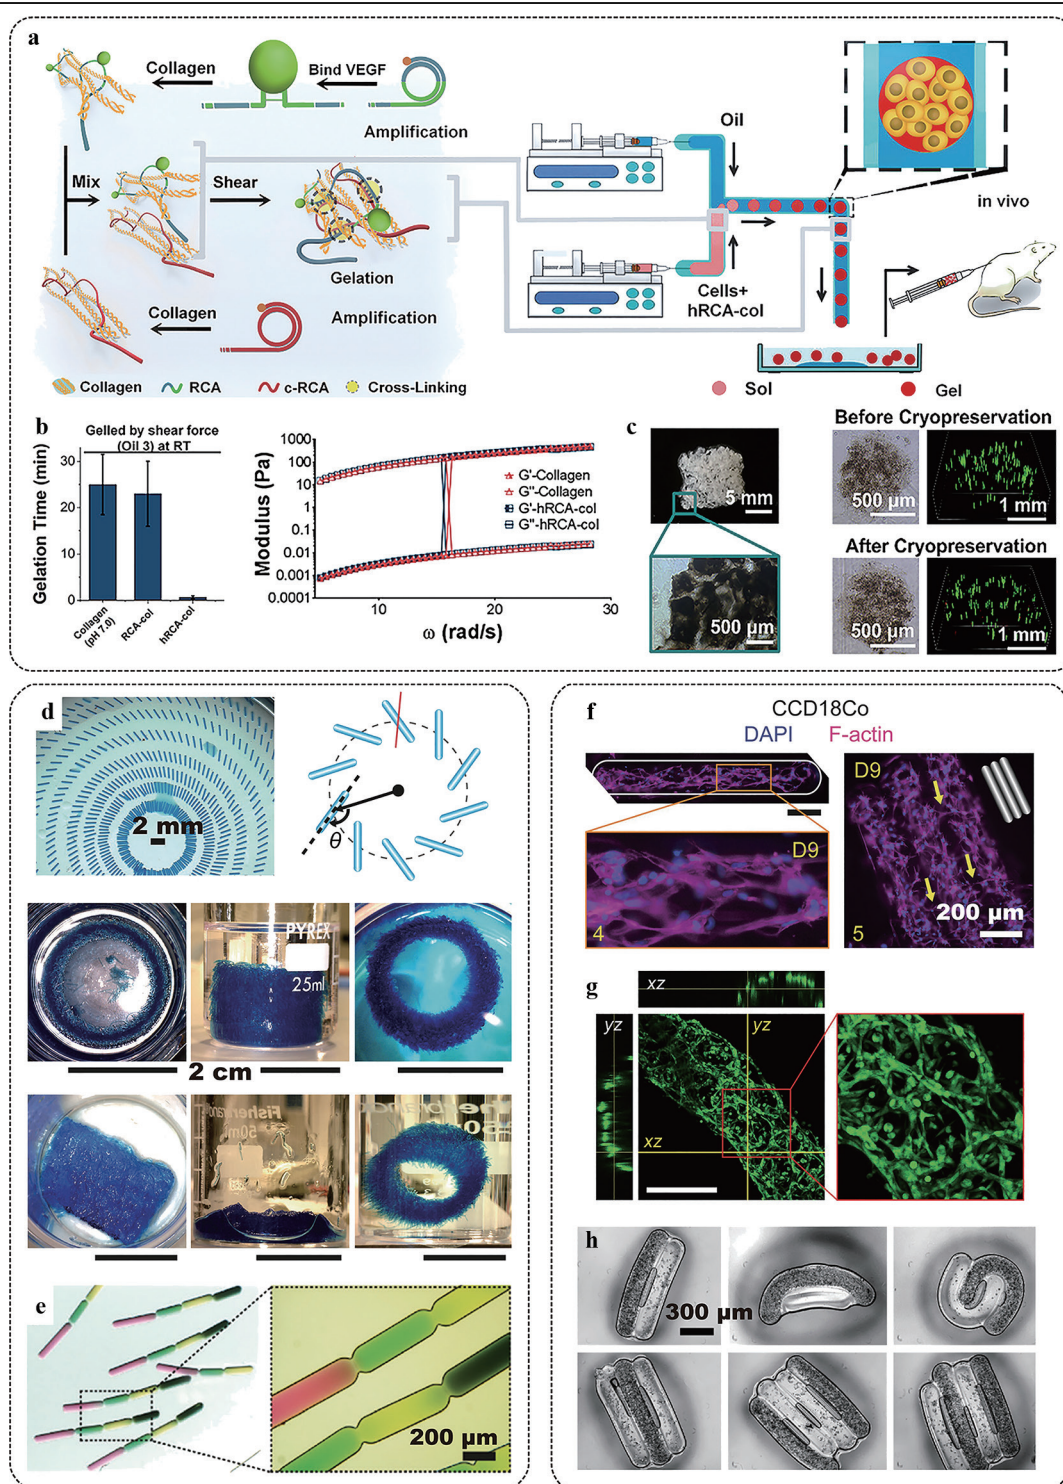


Fig. 3 Manufacturing of ultra-soft microtissues using cascade tubing microfluidics (CTM). **a** Sketch of accelerated manufacturing of ultra-soft collagen gel beads in CTM by adopting the ultra-long single strand RCA-DNA interlocking under shear. **b** Comparison of collagen bead gelation time and shear moduli with (hRCA-col) and without (collagen and RCA-col) the ultra-long RCA-DNA interlocking effect. **c** Images of moulded hRCA-col microbeads and their cryopreservation. Green fluorescence indicates live cells. **d** 2D and 3D patterning of gelatinous microrods manufactured in CTM. **e** Uniform sequences of color-coded microrods. **f** Morphological development of CCD18Co myoblasts in photocrosslinked gelatin methacrylate. **g** Morphological development of NIH-3T3 fibroblasts in a Matrigel rod. Fibroblasts formed luminal organization. **h** Patterned cell laden Matrigel rods driven by hydrophobic effects. Figures adapted from Refs. 38,58,59 with permission.

models, or as building blocks that compose bioprinting inks or tissue complexes⁵⁸ (Fig. 3d–h).

Dynamic moulding of microfibers in microfluidics

Using microchannels as dynamic moulds, moving fluids can be shaped into microfibers via *in situ* crosslinking in the absence of an immiscible fluid^{73–75}. The hydraulic resistance for a flowing fluid is proportional to its friction area with the channel wall and its viscosity, which is a major issue to overcome in system design. To ensure a continuous flow, the friction area must increase with the length of the in-channel flow path, and its viscosity must increase with the crosslinking process. Therefore, microfibre production via *in situ* crosslinking is limited to either rapid crosslinking reactions, where the crosslinking path is dramatically shortened^{73,74}, or addressed via a cascade pumping mechanism, where the resistance is decomposed and overcome in a stepwise pumping manner⁷⁶ (Fig. 4a–c). To shorten the crosslinking path, proteinaceous materials, such as collagen, are mixed with alginate that rapidly crosslinks by chelating with Ca^{2+} , providing mechanical stability for collagen before they are fully shaped^{77,78} (Fig. 4a, b). The channel geometry also contributes to patterning the internal fluid compositions, as the graphene plates are laminated in shallow channel confinement (Fig. 4d).

Collagen promotes cell self-organization within the porous fibrous scaffold, but alginate lacks the proper cell ligation and degradation abilities. Thus, a homogeneous mixture of collagen and alginate in fibrous shapes limits cell movement. Alternatively, collagen is shaped into a fibrous scaffold in combination with alginate, but adopts the core (collagen)-shell (alginate) separation in their cross-section to achieve synergism between the structural reinforcement and the cell remodelling effect⁷³. This allows cell movement along the core and strengthens the fibre modulus of the shell. Culturing cell-laden scaffolds on a chip is an alternative method to obtain a cell-remodelling environment with supreme structural stability⁸¹.

Dynamic moulding of microfibres using electrospinning

Electrospinning^{82,83} is an established technique for manufacturing high-strength fibres spanning a few tens to hundreds of nanometres in width. In the electrospinning process, the jet device is filled with a polymer solution or molten liquid. Positive and negative charges are applied separately to the jet device and the receiver. The polymer droplets at the nozzle are filled with electric charges and receive electric force. When the electric intensity increases to a critical value, the electric force overcomes the surface

tension. The droplet is ejected from the nozzle and is stretched to the receiver. In this process, the solvent is rapidly volatilized, and the polymers become nanometre-wide fibres. Electrospinning has a high production rate. However, this process is not cytocompatible because of the use of organic solvents and/or high temperatures.

3D printing for microtissue engineering with customization

3D Printing technology can produce scaffold structures with customised designs, such as beads, rods, fibres, and complex networks in one system^{84,85}. Microextrusion is widely used in laboratories and has started to prove its potential for industrial use. For soft materials, such as gelatin and its derivatives, the extruded volume can be shaped on the substrate, with a certain level of structure and resolution maintenance⁴⁰. For ultra-soft and slow-gelling materials, such as collagen and fibronectin, the shaping is supported by relatively rigid and fast gelling materials extruded in parallel and within close proximity⁸⁶. This effect can also be achieved by using a microparticle gel slurry as the Bingham fluid support, which behaves as a liquid under shear deformation but recovers to solid-state under free-of-shear conditions⁷⁹ (Fig. 4e). The ultra-soft and fragile liquid is embedded and fixed in the slurry after being extruded. The production of tissue microspheres, fibres, and assembled networks have been proven in the presence of cells.

Alternatively, cells and fibrous scaffolds can be printed separately when the cell suspension is filled into the designed gaps of the scaffold in a layer-by-layer additive process. For example, Lee et al. studied the 3D co-printing of collagen and C2C12 cells⁸⁰. Two extruders, one filled with the supporting material (collagen) and the other filled with a high-concentration cell ink, were used in the co-printing process. When the acidified collagen solution was extruded into the neutral buffer, it was rapidly neutralised, initiated its gelation, and assembled into a construct under tri-axis guidance (Fig. 4f, g).

Photolithography for microtissue engineering with customization

Photocrosslinkable materials, either synthetic or chemically derived natural materials, can be solidified by light radiation in the presence of a photoinitiator. Most initiators are UV light sensitive. Photolithography refers to a scenario in which a designed structure is shaped when the light radiation is patterned⁸⁹. A photolithography system consists of a light source, a container with the substrate and the prepolymer solution, a series of lenses, and a digital micro-mirror device (DMD) or a physical mask projecting

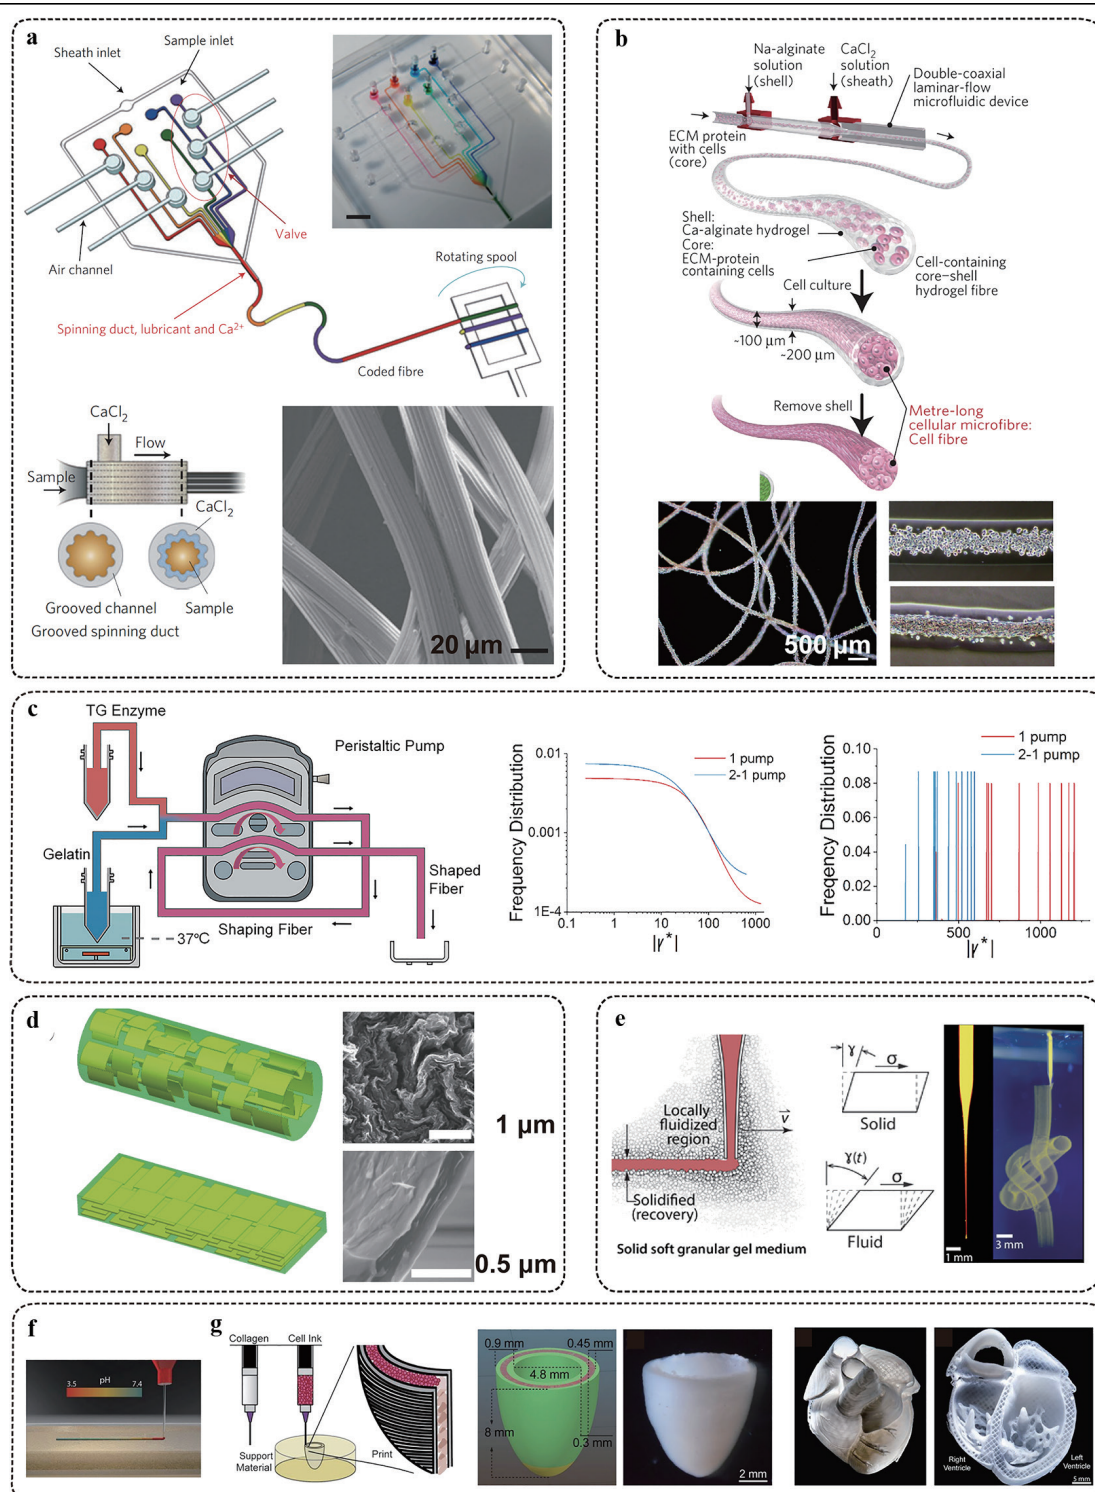


Fig. 4 Manufacturing of soft and ultra-soft tissue fibres with microscale precision. **a** Sketch and images of digital microfluidic fibre synthesizer with coded sequence or surface grooves. **b** Sketch and images of core-shell structured collagen-based tissue fibres. **c** Reducing hydraulic resistance in in-channel fibre gelation by using cascade pumping. The shear levels are significantly reduced by adopting the 2-pumping scheme. **d** Microfluidics-based synthesizer of graphene fibres with defined orientation, modulated by flow topology. **e** Manufacturing of soft fibre-based architecture by using a granular medium (Bingham fluid) support. **f**, **g** Manufacturing of a functional heart model by patterning collagen fibre with *in situ* crosslinking within Bingham fluid buffer **f**. Figures adapted from Refs. 73–76,79,80 with permission.

designed patterns^{87,90,91}. When the radiation pattern is 3D or illuminated via layer-by-layer patterns in a temporal sequence, a 3D structure with defined variation along the *z*-axis is obtained^{92,93}. When photocrosslinking occurs on moving fluids, continuous and reproducible production of coded microbeads is achieved (Fig. 5).

Photolithography is a technique that is supposed to achieve accurate patterning of cell seeding instead of a random distribution. Its early development focused on patterning adhesive proteins on substrates, and cells were introduced via traditional cell-seeding methods after scaffold fabrication⁹⁴. However, recent studies have focused on incorporating cells within the scaffold before crosslinking⁹⁰, thereby improving the cell distribution accuracy, promoting the interaction of cells and scaffolds, and increasing the number of seeded cells. For example, Ma et al. patterned two types of cells using two-step 3D photolithography to mimic the native architecture and cell

composition in hepatic tissue⁸⁷.

Photolithography has advantages over other dimensions. It controls fabrication via external optical signals without invading and disturbing the cell-scaffold interactive environment. It can also conduct scale-up fabrication by enlarging the patterned radiation area, which increases productivity compared to the voxel-based printing techniques⁹⁵, including microextrusion-based and inkjet printing. However, in terms of structural complexity, voxel-based printing retains its competence in engineering tissues composed of multiple phases and cell types.

Challenges and perspectives

Lack of viscoelastic materials that recapitulate the same mechanical properties as the native scaffolds

It has been acknowledged that most extracellular matrix (ECM) materials are viscoelastic¹³, although their

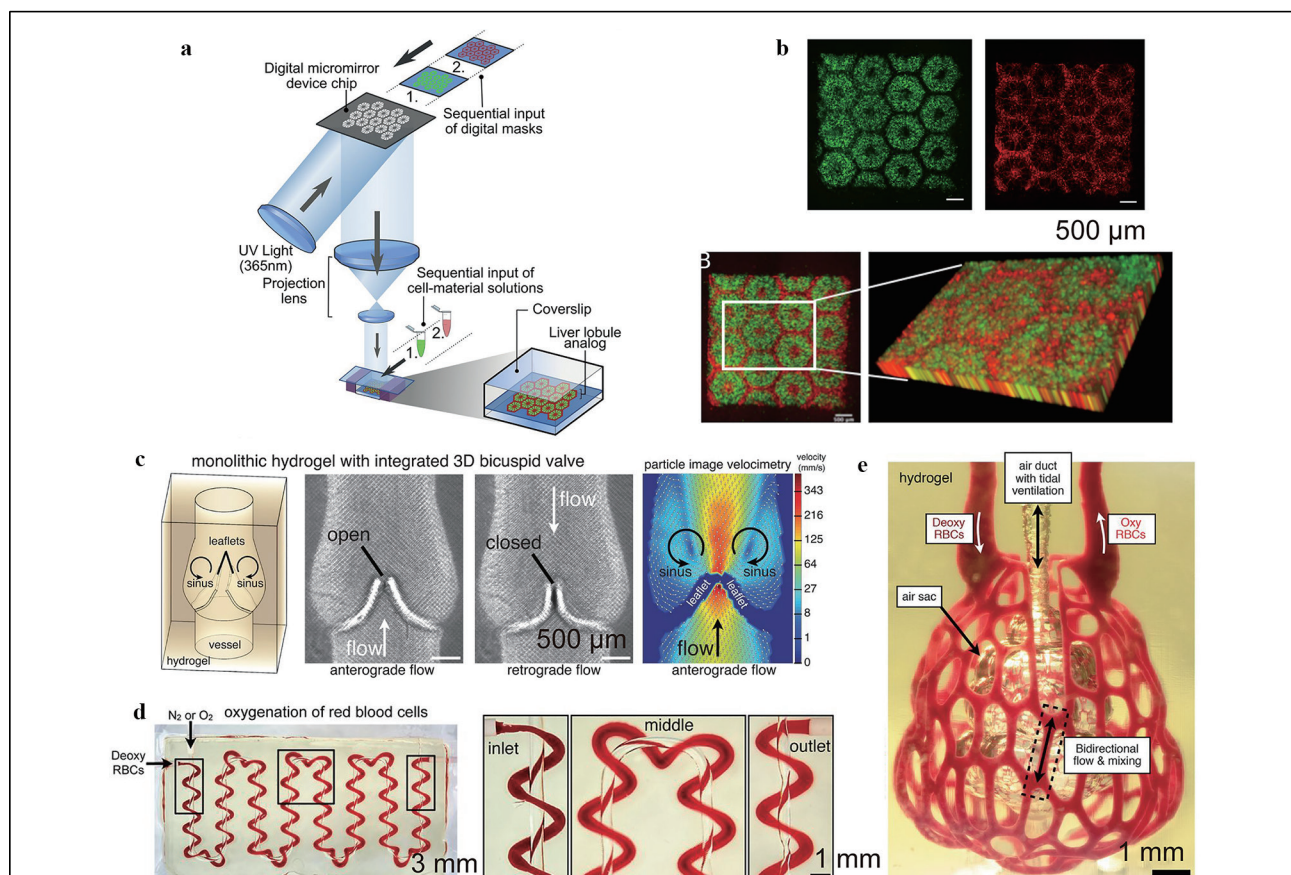


Fig. 5 Photolithography-based additive manufacturing of functional tissues and organ models. **a** Schematic diagram of a two-step 3D bioprinting approach in which hiPSC-HPCs were patterned by the first digital mask followed by the patterning of supporting cells using a second digital mask. **b** 3D reconstruction of the construct showing the patterns of hepatic cells (green) and supporting cells (red). **c** Photolithography-patterned scaffolds with a functional 3D bicuspid valve integrated into the vessel wall under anterograde and retrograde flows. **d** Tessellation of the axial vessel and its encompassing helix along a serpentine pathway. Both passages are perfusable and allow the exchange of oxygen. **e** Photograph of a manufactured scaffold architecture containing the distal lung subunit during red blood cell (RBC) perfusion while the air sac was ventilated with oxygen. Figures adapted from Refs. 87,88 with permission.

properties vary in different tissues. To promote cell-matrix mutual remodelling, the materials used are required to possess proper cell ligation and degradation abilities, as well as appropriate porosity. Naturally derived materials include Matrigel (or basement membrane extracts) and decellularized ECM from animal organs. These materials have superior properties to support cell growth, but due to the inconsistency of their resources, these materials suffer lot-to-lot variance, poor reproducibility, high cost, and may cause immunoreactions after transplantation.

Both elastic and viscous materials are easy to synthesise and customise, but viscoelastic materials analogous to native materials are difficult to produce. Additionally, the replacement materials should replicate the properties of porosity, degradability, and communication with cells, to the extent that they are comparable to natural materials. Its scalable production is critical for both basic research and translational applications. The combination of synthetic polymers in conjugation with short peptides is promising, particularly in ultra-large molecular organisations.

Engineering methods for viscoelastic soft materials

Although we summarised the methods capable of engineering soft microtissues, their performance with regard to engineering viscoelastic materials is limited in many aspects. For example, photolithography is limited to photocrosslinkable materials, and flow lithography requires the microstructures to be persistent against flow-induced shear deformation; microextrusion suffers from resolution loss resulting from slow crosslinking in the absence of channel confinement, or friction-induced structural loss when crosslinked in-channel. In the removal of surfactants using microfluidic droplets as structural templates, shear forces during washing and phase transfer would result in the collision and collapse of the fragile microbeads. Cascade tubing microfluidics (CTM) in the absence of surfactants eliminates the need for repeated washing and eases phase transfer, but the use of oil to disperse the cell suspension droplets may result in oil residues and also introduces extra steps, thereby increasing the cost of operation. Novel engineering methods for engineering ultra-soft and viscoelastic materials are in high demand.

Production conflict in the laboratory and scale-up

Lastly, the capacity for live tissue engineering with microscale precision always faces a conflict between laboratory and industrial needs. Both microfluidics- and 3D bioprinting-based engineering techniques exhibit superior performance as state of the art demonstrations. Owing to their intrinsic limitations, a single module set has a limited production ability. Numbering up the running modules can

scale-up production, but the cost and high-parallel control emerge as new issues. Meanwhile, the miniaturisation of the control modules in the aforementioned techniques is a common challenge. The 3D printed tissues have larger scales but can be regarded as scaled-up examples of microtissues in an ordered assembly. Further scaling-up of the printing modules might pave the way toward industrial manufacturing of soft and ultra-soft tissues.

In conclusion, engineering soft and ultra-soft scaffolds in a cytocompatible and yield-friendly manner has fundamental impacts on both basic and translational medicine. Techniques such as these are expected to offer breakthroughs and accelerate disease studies, drug discoveries, personalised medicine, and regenerative therapies. Its interdisciplinary nature requires joint inputs from materials, biology, chemistry, medicine, and mechanical and electronic engineering to overcome the modular challenges.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (Grant Number: 61971255), Shenzhen Bay Laboratory Fund (Grant Number: SZBL2020090501014), and Shenzhen Science and Technology Innovation Committee (Grant Number: KCXFZ202002011010508).

Author contributions

S.M. and Z.W. conceived the concept and outlined the review. S.M., J.W., X.T., Z.W., and J.L. prepared the manuscript.

Conflict of interest

The authors declare no conflict of interest.

Received: 02 December 2020 Revised: 19 January 2021 Accepted: 23 February 2021

Accepted article preview online: 03 March 2021

Published online: 10 April 2021

References

1. Jedrzejczak-Silicka, M. History of cell culture. in *New Insights into Cell Culture Technology* (ed Gowder, S. J. T.) (IntechOpen, London. 2017).
2. Elsdale, T. & Bard, J. Collagen substrata for studies on cell behavior. *Journal of Cell Biology* **54**, 626-637 (1972).
3. Thiele, J. et al. 25th anniversary article: designer hydrogels for cell cultures: a materials selection guide. *Advanced Materials* **26**, 125-147 (2014).
4. Reed, J. et al. In situ mechanical interferometry of matrigel films. *Langmuir* **25**, 36-39 (2009).
5. Orkin, R. W. et al. A murine tumor producing a matrix of basement membrane. *The Journal of Experimental Medicine* **145**, 204-220 (1977).
6. Benton, G. et al. Matrigel: from discovery and ECM mimicry to assays and models for cancer research. *Advanced Drug Delivery Reviews* **79-80**, 3-18 (2014).
7. Kwee, B. J. & Mooney, D. J. Biomaterials for skeletal muscle tissue engineering. *Current Opinion in Biotechnology* **47**, 16-22 (2017).
8. Moroni, L. et al. Biofabrication: a guide to technology and terminology. *Trends in Biotechnology* **36**, 384-402 (2018).

9. Loebel, C. & Burdick, J. A. Engineering stem and stromal cell therapies for musculoskeletal tissue repair. *Cell Stem Cell* **22**, 325-339 (2018).
10. Moroni, L. et al. Biofabrication strategies for 3D in vitro models and regenerative medicine. *Nature Reviews Materials* **3**, 21-37 (2018).
11. Juliano, R. L. & Haskill, S. Signal transduction from the extracellular matrix. *The Journal of Cell Biology* **120**, 577-585 (1993).
12. Pelham, R. J. Jr. & Wang, Y. L. Cell locomotion and focal adhesions are regulated by substrate flexibility. *Proceedings of the National Academy of Sciences of the United States of America* **94**, 13661-13665 (1997).
13. Chaudhuri, O. et al. Effects of extracellular matrix viscoelasticity on cellular behaviour. *Nature* **584**, 535-546 (2020).
14. Hadden, W. J. et al. Stem cell migration and mechanotransduction on linear stiffness gradient hydrogels. *Proceedings of the National Academy of Sciences of the United States of America* **114**, 5647-5652 (2017).
15. Cosgrove, B. D. et al. N-cadherin adhesive interactions modulate matrix mechanosensing and fate commitment of mesenchymal stem cells. *Nature Materials* **15**, 1297-1306 (2016).
16. Darnell, M. et al. Material microenvironmental properties couple to induce distinct transcriptional programs in mammalian stem cells. *Proceedings of the National Academy of Sciences of the United States of America* **115**, E8368-E8377 (2018).
17. Engler, A. J. et al. Matrix elasticity directs stem cell lineage specification. *Cell* **126**, 677-689 (2006).
18. Soofi, S. S. et al. The elastic modulus of Matrigel™ as determined by atomic force microscopy. *Journal of Structural Biology* **167**, 216-219 (2009).
19. Lou, J. Z. et al. Stress relaxing hyaluronic acid-collagen hydrogels promote cell spreading, fiber remodeling, and focal adhesion formation in 3D cell culture. *Biomaterials* **154**, 213-222 (2018).
20. Chaudhuri, O. et al. Hydrogels with tunable stress relaxation regulate stem cell fate and activity. *Nature Materials* **15**, 326-334 (2016).
21. Garreta, E. et al. Fine tuning the extracellular environment accelerates the derivation of kidney organoids from human pluripotent stem cells. *Nature Materials* **18**, 397-405 (2019).
22. Li, Y. W. et al. Volumetric compression induces intracellular crowding to control intestinal organoid growth via wnt/ β -catenin signaling. *Cell Stem Cell* **28**, 63-78.e7 (2021).
23. Lawlor, K. T. et al. Cellular extrusion bioprinting improves kidney organoid reproducibility and conformation. *Nature Materials*, **20**, 260-271 (2021).
24. Chiou, G. et al. Scaffold architecture and matrix strain modulate mesenchymal cell and microvascular growth and development in a time dependent manner. *Cellular and Molecular Bioengineering* **13**, 507-526 (2020).
25. Mondal, G., Barui, S. & Chaudhuri, A. The relationship between the cyclic-RGDFK ligand and $\alpha\text{v}\beta 3$ integrin receptor. *Biomaterials* **34**, 6249-6260 (2013).
26. Lamshead, J. W. et al. Long-term maintenance of human pluripotent stem cells on cRGDFK-presenting synthetic surfaces. *Scientific Reports* **8**, 701 (2018).
27. Farach-Carson, M. C. & Carson, D. D. Perlecan—a multifunctional extracellular proteoglycan scaffold. *Glycobiology* **17**, 897-905 (2007).
28. Furue, M. K. et al. Heparin promotes the growth of human embryonic stem cells in a defined serum-free medium. *Proceedings of the National Academy of Sciences of the United States of America* **105**, 13409-13414 (2008).
29. Klim, J. R. et al. A defined glycosaminoglycan-binding substratum for human pluripotent stem cells. *Nature Methods* **7**, 989-994 (2010).
30. Musah, S. et al. Glycosaminoglycan-binding hydrogels enable mechanical control of human pluripotent stem cell self-renewal. *ACS Nano* **6**, 10168-10177 (2012).
31. Nowak, M. et al. Modular GAG-matrices to promote mammary epithelial morphogenesis in vitro. *Biomaterials* **112**, 20-30 (2017).
32. Juliar, B. A. et al. Cell-mediated matrix stiffening accompanies capillary morphogenesis in ultra-soft amorphous hydrogels. *Biomaterials* **230**, 119634 (2020).
33. Khademhosseini, A. & Langer, R. A decade of progress in tissue engineering. *Nature Protocols* **11**, 1775-1781 (2016).
34. Berthiaume, F., Maguire, T. J. & Yarmush, M. L. Tissue engineering and regenerative medicine: history, progress, and challenges. *Annual Review of Chemical and Biomolecular Engineering* **2**, 403-430 (2011).
35. Yin, X. L. et al. Engineering stem cell organoids. *Cell Stem Cell* **18**, 25-38 (2016).
36. Lancaster, M. A. & Knoblich, J. A. Organogenesis in a dish: modeling development and disease using organoid technologies. *Science* **345**, 1247125 (2014).
37. Echave, M. C. et al. Gelatin as biomaterial for tissue engineering. *Current Pharmaceutical Design* **23**, 3567-3584 (2017).
38. Ma, S. H. et al. Gel microrods for 3D tissue printing. *Advanced Biosystems* **1**, 1700075 (2017).
39. Nichol, J. W. et al. Cell-laden microengineered gelatin methacrylate hydrogels. *Biomaterials* **31**, 5536-5544 (2010).
40. Kolesky, D. B. et al. Three-dimensional bioprinting of thick vascularized tissues. *Proceedings of the National Academy of Sciences of the United States of America* **113**, 3179-3184 (2016).
41. Oryan, A. et al. Chemical crosslinking of biopolymeric scaffolds: current knowledge and future directions of crosslinked engineered bone scaffolds. *International Journal of Biological Macromolecules* **107**, 678-688 (2018).
42. Gattazzo, F. et al. Gelatin-genipin-based biomaterials for skeletal muscle tissue engineering. *Journal of Biomedical Materials Research Part B: Applied Biomaterials* **106**, 2763-2777 (2018).
43. Kitagawa, T. et al. Three-dimensional cell seeding and growth in radial-flow perfusion bioreactor for in vitro tissue reconstruction. *Biotechnology and Bioengineering* **93**, 947-954 (2006).
44. Olivares, A. L. & Lacroix, D. Simulation of cell seeding within a three-dimensional porous scaffold: a fluid-particle analysis. *Tissue Engineering Part C: Methods* **18**, 624-631 (2012).
45. Mao, D. et al. Bio-orthogonal click reaction-enabled highly specific in situ cellularization of tissue engineering scaffolds. *Biomaterials* **230**, 119615 (2020).
46. Bidarra, S. J., Barrias, C. C. & Granja, P. L. Injectable alginate hydrogels for cell delivery in tissue engineering. *Acta Biomaterialia* **10**, 1646-1662 (2014).
47. Kuo, C. K. & Ma, P. X. Ionically crosslinked alginate hydrogels as scaffolds for tissue engineering: part 1. Structure, gelation rate and mechanical properties. *Biomaterials* **22**, 511-521 (2001).
48. Tibbitts, S. 4D printing: multi-material shape change. *Architectural Design* **84**, 116-121 (2014).
49. Galarraga, J. H. & Burdick, J. A. Moving hydrogels to the fourth dimension. *Nature Materials* **18**, 914-915 (2019).
50. Burdick, J. A. & Murphy, W. L. Moving from static to dynamic complexity in hydrogel design. *Nature Communications* **3**, 1269 (2012).
51. Khetan, S. et al. Degradation-mediated cellular traction directs stem cell fate in covalently crosslinked three-dimensional hydrogels. *Nature Materials* **12**, 458-465 (2013).
52. Caiazzo, M. et al. Defined three-dimensional microenvironments boost induction of pluripotency. *Nature Materials* **15**, 344-352 (2016).
53. Purcell, B. P. et al. Injectable and bioresponsive hydrogels for on-demand matrix metalloproteinase inhibition. *Nature Materials* **13**, 653-661 (2014).
54. Ye, H. Y. et al. Polyester elastomers for soft tissue engineering.

- Chemical Society Reviews* **47**, 4545-4580 (2018).
55. Matsunaga, Y. T., Morimoto, Y. & Takeuchi, S. Molding cell beads for rapid construction of macroscopic 3D tissue architecture. *Advanced Materials* **23**, H90-H94 (2011).
 56. Morimoto, Y., Tanaka, R. & Takeuchi, S. Construction of 3D, layered skin, micro-sized tissues by using cell beads for cellular function analysis. *Advanced Healthcare Materials* **2**, 261-265 (2013).
 57. Wen, Y. J. et al. Spinal cord injury repair by implantation of structured hyaluronic acid scaffold with PLGA microspheres in the rat. *Cell and Tissue Research* **364**, 17-28 (2016).
 58. Zhao, H. R. et al. Microfluidic synthesis of injectable angiogenic microgels. *Cell Reports Physical Science* **1**, 100047 (2020).
 59. Ma, S. H. Microfluidics tubing as a synthesizer for ordered microgel networks. *Soft Matter* **15**, 3848-3853 (2019).
 60. Shang, L. R., Cheng, Y. & Zhao, Y. J. Emerging droplet microfluidics. *Chemical Reviews* **117**, 7964-8040 (2017).
 61. Li, W. et al. Microfluidic fabrication of microparticles for biomedical applications. *Chemical Society Reviews* **47**, 5646-5683 (2018).
 62. Ma, S. et al. Monodisperse collagen-gelatin beads as potential platforms for 3D cell culturing. *Journal of Materials Chemistry. B* **1**, 5128-5136 (2013).
 63. Wang, W. et al. Hole-shell microparticles from controllably evolved double emulsions. *Angewandte Chemie International Edition* **52**, 8084-8087 (2013).
 64. Deng, N. N. et al. Wetting-induced formation of controllable monodisperse multiple emulsions in microfluidics. *Lab on a Chip* **13**, 4047-4052 (2013).
 65. Ma, S. H. et al. Fabrication of microgel particles with complex shape via selective polymerization of aqueous two-phase systems. *Small* **8**, 2356-2360 (2012).
 66. Chu, L. Y. et al. Controllable monodisperse multiple emulsions. *Angewandte Chemie International Edition* **46**, 8970-8974 (2007).
 67. Ma, S. H., Huck, W. T. S. & Balabani, S. Deformation of double emulsions under conditions of flow cytometry hydrodynamic focusing. *Lab on a Chip* **15**, 4291-4301 (2015).
 68. Ma, S. H. et al. On the flow topology inside droplets moving in rectangular microchannels. *Lab on a Chip* **14**, 3611-3620 (2014).
 69. Ma, S. H. et al. The microenvironment of double emulsions in rectangular microchannels. *Lab on a Chip* **15**, 2327-2334 (2015).
 70. Sorushanova, A. et al. The collagen suprafamily: from biosynthesis to advanced biomaterial development. *Advanced Materials* **31**, 1801651 (2019).
 71. Singh, P., Carraher, C. & Schwarzbauer, J. E. Assembly of fibronectin extracellular matrix. *Annual Review of Cell and Developmental Biology* **26**, 397-419 (2010).
 72. Bonnans, C., Chou, J. & Werb, Z. Remodelling the extracellular matrix in development and disease. *Nature Reviews Molecular Cell Biology* **15**, 786-801 (2014).
 73. Onoe, H. et al. Metre-long cell-laden microfibres exhibit tissue morphologies and functions. *Nature Materials* **12**, 584-590 (2013).
 74. Kang, E. et al. Digitally tunable physicochemical coding of material composition and topography in continuous microfibres. *Nature Materials* **10**, 877-883 (2011).
 75. Xin, G. Q. et al. Microfluidics-enabled orientation and microstructure control of macroscopic graphene fibres. *Nature Nanotechnology* **14**, 168-175 (2019).
 76. Cao, Y. X. et al. Cascade pumping overcomes hydraulic resistance and moderates shear conditions for slow gelatin fiber shaping in narrow tubes. *iScience* **23**, 101228 (2020).
 77. An, D. et al. Designing a retrievable and scalable cell encapsulation device for potential treatment of type 1 diabetes. *Proceedings of the National Academy of Sciences of the United States of America* **115**, E263-E272 (2018).
 78. Jun, Y. et al. Microfluidics-generated pancreatic islet microfibers for enhanced immunoprotection. *Biomaterials* **34**, 8122-8130 (2013).
 79. Bhattacharjee, T. et al. Writing in the granular gel medium. *Science Advances* **1**, e1500655 (2015).
 80. Lee, A. et al. 3D bioprinting of collagen to rebuild components of the human heart. *Science* **365**, 482-487 (2019).
 81. Kunze, A. et al. Micropatterning neural cell cultures in 3D with a multi-layered scaffold. *Biomaterials* **32**, 2088-2098 (2011).
 82. Muerza-Cascante, M. L. et al. Melt electrospinning and its technologization in tissue engineering. *Tissue Engineering Part B: Reviews* **21**, 187-202 (2015).
 83. Hong, J. et al. Cell-electrospinning and its application for tissue engineering. *International Journal of Molecular Sciences* **20**, 6208 (2019).
 84. Murphy, S. V. & Atala, A. 3D bioprinting of tissues and organs. *Nature Biotechnology* **32**, 773-785 (2014).
 85. Murphy, S. V., De Coppi, P. & Atala, A. Opportunities and challenges of translational 3D bioprinting. *Nature Biomedical Engineering* **4**, 370-380 (2020).
 86. Kang, H. W. et al. A 3D bioprinting system to produce human-scale tissue constructs with structural integrity. *Nature Biotechnology* **34**, 312-319 (2016).
 87. Ma, X. Y. et al. Deterministically patterned biomimetic human iPSC-derived hepatic model via rapid 3D bioprinting. *Proceedings of the National Academy of Sciences of the United States of America* **113**, 2206-2211 (2016).
 88. Grigoryan, B. et al. Multivascular networks and functional intravascular topologies within biocompatible hydrogels. *Science* **364**, 458-464 (2019).
 89. Bajaj, P. et al. 3D biofabrication strategies for tissue engineering and regenerative medicine. *Annual Review of Biomedical Engineering* **16**, 247-276 (2014).
 90. Soman, P. et al. Digital microfabrication of user-defined 3D microstructures in cell-laden hydrogels. *Biotechnology and Bioengineering* **110**, 3038-3047 (2013).
 91. Hribar, K. C. et al. Light-assisted direct-write of 3D functional biomaterials. *Lab on a Chip* **14**, 268-275 (2014).
 92. Melchels, F. P., Feijen, J. & Grijpma, D. W. A review on stereolithography and its applications in biomedical engineering. *Biomaterials* **31**, 6121-6130 (2010).
 93. Bhattacharjee, N. et al. Desktop-stereolithography 3D-Printing of a poly(dimethylsiloxane)-based material with sylgard-184 properties. *Advanced Materials* **30**, 1800001 (2018).
 94. Bhatia, S. N. et al. Effect of cell-cell interactions in preservation of cellular phenotype: cocultivation of hepatocytes and nonparenchymal cells. *The FASEB Journal* **13**, 1883-1900 (1999).
 95. Li, X. D. et al. Inkjet bioprinting of biomaterials. *Chemical Reviews* **120**, 10793-10833 (2020).